

THE STRUCTURAL PROPERTIES OF ZnO/TiO₂ BILAYER THIN FILM AS PHOTOANODE

Fatiatun^{1,2}, A.B. Suriani^{1,2*}, A. Mohamed^{1,3}, N. Hashim^{1,3},
M.H. Mamat^{4,5} and M.F. Malek^{4,5}
*e-mail: absuriani@yahoo.com

¹Nanotechnology Research Centre,

²Department of Physics,

³Department of Chemistry,

Faculty of Science and Mathematics,

Universiti Pendidikan Sultan Idris, 35900 Tanjung Malim, Perak, Malaysia.

⁴NANO-Electronic Centre (NET), Faculty of Electrical Engineering,
Universiti Teknologi MARA, 40450 Shah Alam, Selangor, Malaysia.

⁵NANO-SciTech Centre (NST), Institute of Science (IOS),
Universiti Teknologi MARA, 40450 Shah Alam, Selangor, Malaysia.

ABSTRACT

The ZnO/TiO₂ bilayer was fabricated on the fluorine-doped tin oxide (FTO) substrate. The ZnO nanorods and TiO₂ nanoparticles were developed as photoanode material that were fabricated by using sol-gel immersion and squeegee method. The structure of ZnO/TiO₂ bilayer showed a good properties for photoanode in DSSCs application. The ZnO/TiO₂ bilayer has large surface area that could increase a dye loading and performance of photoanode. Meanwhile, the micro-Raman spectra of ZnO/TiO₂ bilayer indicated a good crystallinity. Therefore, the ZnO/TiO₂ bilayer showed a good structure for photoanode in DSSCs application.

Key words: ZnO nanorods, TiO₂ nanoparticles, ZnO/TiO₂ bilayer, Photoanode

ABSTRAK

Lapisan ZnO/TiO₂ difabrikasi di atas substrat oksida timah yang di doping florin (FTO). Batang nano ZnO dan partikel nano TiO₂ dikembangkan sebagai material fotoanoda yang difabrikasi menggunakan metode pencelupan sol-gel dan *squeegee*. Struktur lapisan ZnO/TiO₂ menunjukkan sifat fotoanoda yang baik dalam aplikasi DSSCs. Lapisan ZnO/TiO₂ memiliki luas permukaan yang besar yang bisa meningkatkan muatan *dye* dan performa fotoanoda. Sedangkan spktrum mikro-Raman lapisan ZnO/TiO₂ mengindikasikan kristalinitas yang bagus. Oleh karena itu, lapisan ZnO/TiO₂ menunjukkan struktur yang baik untuk fotoanoda di dalam aplikasi DSSCs.

Kata Kunci: batang nano ZnO, partikel nano TiO₂, lapisan ZnO/TiO₂, fotoanoda

INTRODUCTION

Recently, the semiconductors such as zinc oxide (ZnO) and titanium dioxide (TiO₂) have received wide attention due to their outstanding optical and electrical properties (Kwiatkowski, et al, 2015). The semiconductor materials are included in wide band gap (~3 eV) and good absorption in UV range. The band gap of ZnO is around ~3.37 eV (Wu, et al, 2013) and TiO₂ is around ~3.2 eV (Lee, et al, 2010). The ZnO is widely used in photovoltaic devices due to its high electron mobility of 200-300 cm²Vs⁻¹ for bulk ZnO, meanwhile for single crystal ZnO nanowires its electron mobility is much higher at ~1000 cm²Vs⁻¹ (Ozgur, et al, 2005). For the TiO₂, it has low electron mobility (0.1-4 cm²Vs⁻¹) (Tang, et al, 1994). The ZnO is a good candidate as photoanode in dye sensitized solar cells (DSSCs) application due to its low cost, nontoxicity

(Umar, et al, 2008), strong exciton binding energy (60 meV) (Kim, et al, 2010), chemical and thermal stability (Zeng, et al, 2009). However, ZnO has a low energy conversion efficiency in photovoltaic performance.

Therefore, the TiO₂ is also developed as photoanode material because of its high performance in energy conversion efficiency. The TiO₂ is used to improve the properties of ZnO and increase the performance of photoanode in DSSCs application. Then, the TiO₂ is fabricated on the ZnO thin film to produce photoanode properties much better. The structures of ZnO such as nanorods (Wu, et al, 2013), nanowires (Fan, et al 2013), nanotubes (Han, et al, 2010) and nanosheets (Li, et al, 2012) are usual morphology used as photoanode in DSSCs application. However, among all

these the ZnO nanorods structure are widely used in photoanode due to their high energy conversion efficiency and better electron transport (Kislyuk, et al, 2008). The ZnO nanorods are usually grown on the seeded catalyst such as magnesium (Mg) (Zhou, et al, 2011), aluminum (Al) (Malek, et al, 2016) and aurum (Au) (Xu, et al, 2013). Among those mentioned seeded catalysts, Mg is preferable catalyst for ZnO nanorods growth due to its similar ionic radii (0.72 Å) to Zn²⁺ (0.74 Å) which later gives less lattice distortion when Zn²⁺ is replaced with Mg²⁺ (Lien, et al, 2014).

The ZnO nanorods can be grown by using sol-gel immersion method (Malek, et al, 2013), solvothermal (Wu, et al, 2013) and hydrothermal (Tan, et al, 2013). Among these methods, sol-gel immersion shows the best method to grow aligned ZnO nanorods due to its low cost and simple fabrication. Afterwards, the TiO₂ nanoparticles can be fabricated either by using squeegee method (Zainun, et al, 2012), hydrothermal (Yune, et al, 2013) or screen printing (Valsaraj, et al, 2016). However, the squeegee method is preferred to fabricate TiO₂ nanoparticles on ZnO nanorods in conjunction of its simple fabrication and low cost production. In this paper, the ZnO/TiO₂ bilayer as photoanode was fabricated on FTO substrate. The structural properties of ZnO/TiO₂ bilayer were carried out by using field emission scanning microscopy (FESEM), energy dispersive X-ray (EDX) and micro-Raman spectroscopy. From the analysis done, it shows that the ZnO/TiO₂ bilayer is potential to be used as photoanode for DSSCs application.

MATERIALS AND METHODS

The ZnO/TiO₂ bilayer fabrication involved 3 steps. (1) First, the

magnesium zinc oxide (MgZnO) seeded catalyst was fabricated by mixing zinc acetate dehydrate ($\text{Zn}(\text{CH}_3\text{COO})_2 \cdot 2\text{H}_2\text{O}$; 99.5% purity; EMSURE) as precursor and magnesium nitrate hexahydrate ($\text{Zn}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}$; 99% purity; Across Organic) as dopant which were mixed into 2-methoxyethanol ($\text{C}_3\text{H}_8\text{O}_2$) solvent. Then, monoethanolamine ($\text{C}_2\text{H}_7\text{NO}$) as stabilizer was added in the solution. Afterwards, the 0.4 M of MgZnO solution was prepared by using 0.88 g of zinc acetate dehydrate, 0.44 g of magnesium nitrate hexahydrate and the 0.25 ml of monoethanolamine then mixed with 10 ml of 2-methoxyethanol. The MgZnO solution was then coated on $2 \times 1 \text{ cm}^2$ FTO substrate by using spin coating technique and annealed at 500°C for 1 hour.

(2) Second, the ZnO nanorods were grown on MgZnO seeded catalyst by using sol-gel immersion method (Suriani, et al, 2016). The ZnO solution was prepared by mixing of 2.975 g zinc nitrate hexahydrate and 1.409 g of hexamethylenetetramine (HMT) into 200 ml of DI water. The ZnO nanorods were synthesized in water bath for 4 hours at 95°C . Then, the ZnO was annealed at 500°C for 1 hour. (3) Next, the TiO₂ nanoparticles on ZnO nanorods (ZnO/TiO₂ bilayer) was coated by using squeegee method (Yune, et al, 2013). The TiO₂ paste was prepared from 3.5 g of commercial titanium (IV) oxide nanopowder (Sigma Aldrich, particle size $\sim 21 \text{ nm}$), 0.5 ml titanium tetraisopropoxide (TTIP) and 15 ml ethanol. The ZnO/TiO₂ bilayer were then annealed at 450°C for 1 hour. The ZnO/TiO₂ bilayer was characterized by using FESEM-Hitachi Su8020, EDX-Horiba EMAX and micro-Raman spectroscopy (Renishaw InVia micro-Raman System).

RESULTS AND DISCUSSIONS

The FESEM images (Fig. 1) show the morphology of ZnO/TiO₂ bilayer by sol-gel immersion and squeegee method. The MgZnO image shown in Fig. 1(a) that demonstrated nanoparticles structure and the grains size were around 15-35 nm. Meanwhile, the white agglomerations of MgZnO nanoparticles in the surface were shown by the arrow and these were caused by the inhomogeneous MgZnO solution. Fig. 1(b)-(c) show the top and side view of vertically aligned ZnO nanorods that were grown on MgZnO nanoparticles. Then, the existence of HMT in the ZnO solution produced ZnO with a hexagonal-shaped. The diameter and thickness of ZnO nanorods were around 675-794 nm and 2.89-5.13 μm , respectively. The different thickness of ZnO nanorods was believed and resulted from an uneven of MgZnO seeded catalyst (Suriani, et al, 2015). The thickness of MgZnO seeded catalyst was measured to be around 1.15 μm as shown in Fig. 1(c).

Fig. 1(d)-(e) show the top and side view of ZnO/TiO₂ bilayer where the TiO₂ nanoparticles were coated on top of ZnO nanorods. The approximate thickness of TiO₂ nanoparticles on ZnO nanorods was measured to be at around 9.72-13.2 μm . However, the overall TiO₂ nanoparticles thickness were seen to be uneven which may be attributed to low amount of dye adsorption on the TiO₂ surface when used as photoanode later on. The photo-excitation of electrons in the photoanode was influenced by the amounts of dye adsorption. Therefore, low dye adsorption by uneven TiO₂ sample may results in low energy conversion efficiency if they are applied for DSSCs application. Nonetheless, large surface area of TiO₂ itself was believed that it

could absorb dye optimally as compared

to pristine ZnO as photoanode.

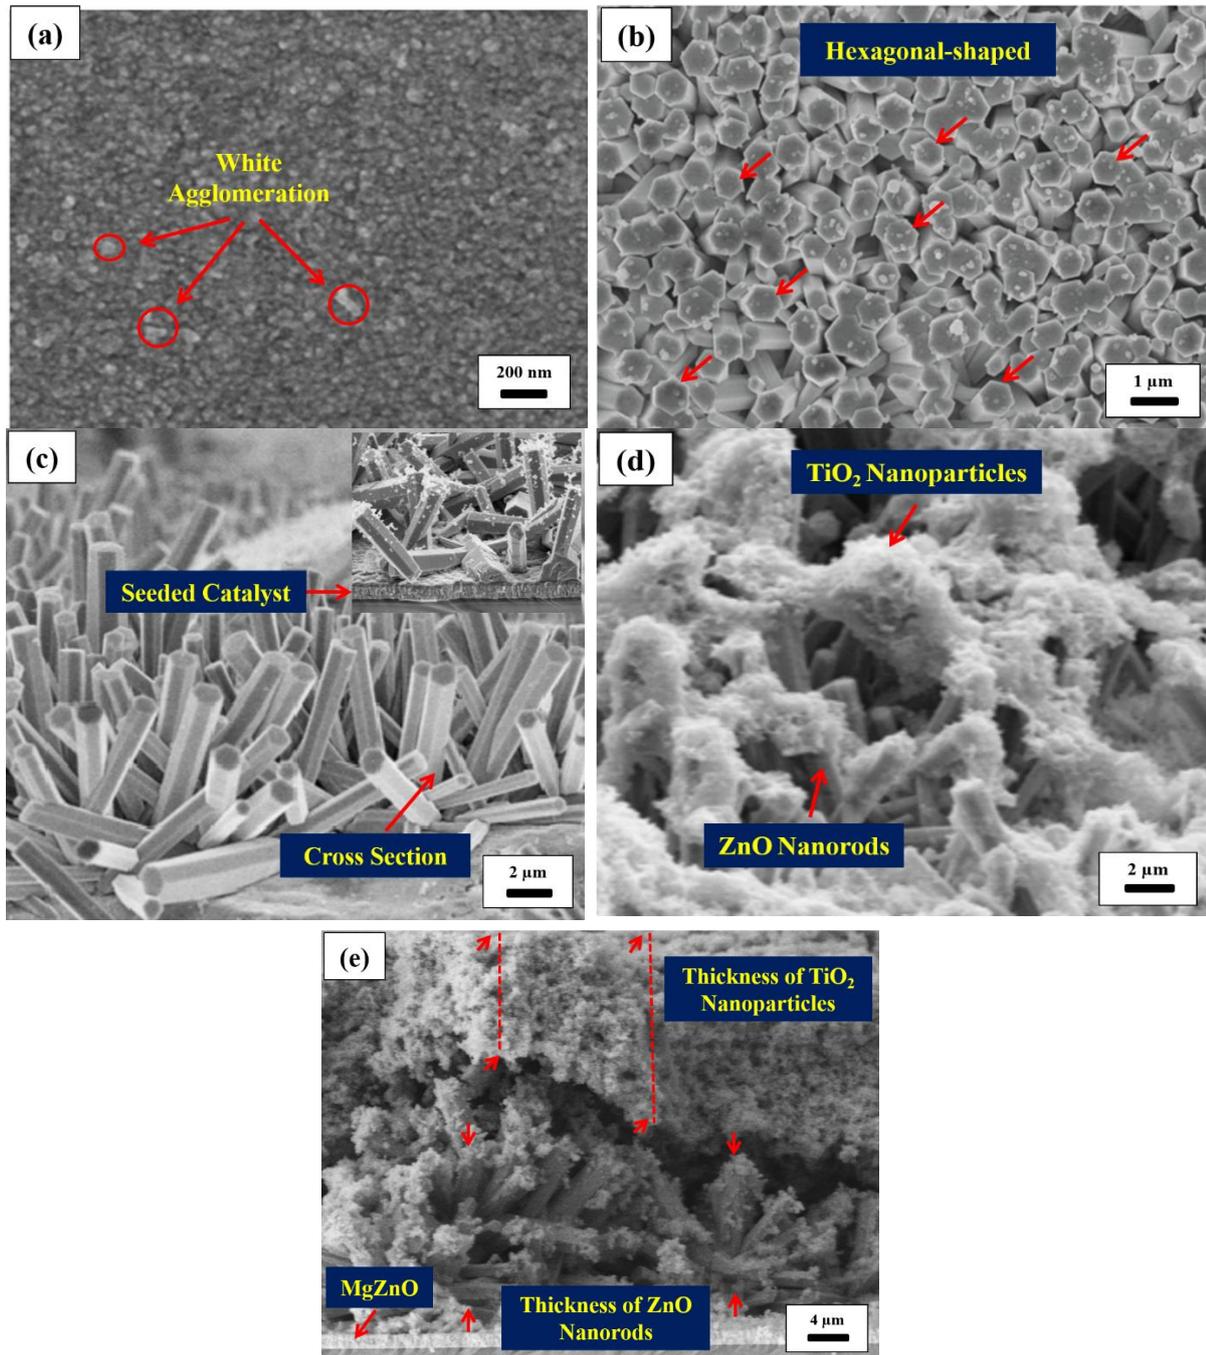


Fig. 1. FESEM images of (a) MgZnO seeded catalyst, (b) top and (c) side view of ZnO nanorods, (d) top and (e) side view of ZnO/TiO₂ bilayer.

Next, the composition of ZnO/TiO₂ bilayer was examined by using EDX as shown in Fig. 2. Fig. 2(a) shows the EDX spectra of MgZnO seeded catalyst that has atomic % of

~5.28% Mg, ~16.21% Zn and ~74.48% O. These results were consistent with the previous research (Suriani, et al, 2015). Meanwhile, the EDX spectra of ZnO is shown in Fig. 2(b) that has

atomic content of ~39.61% Zn, ~0.85% Mg and ~59.55% O. Fig 2(c) shows the EDX spectra of ZnO/TiO₂ bilayer which confirmed the Mg, Zn, Ti and O in the ZnO/TiO₂ bilayer thin film. This result proved that the highest atomic content

was Ti (~27.69%). The highest atomic % of TiO₂ content detected from EDX consistent with FESEM analysis as Ti was thicker than Zn with the difference thickness value around 4-8 μm.

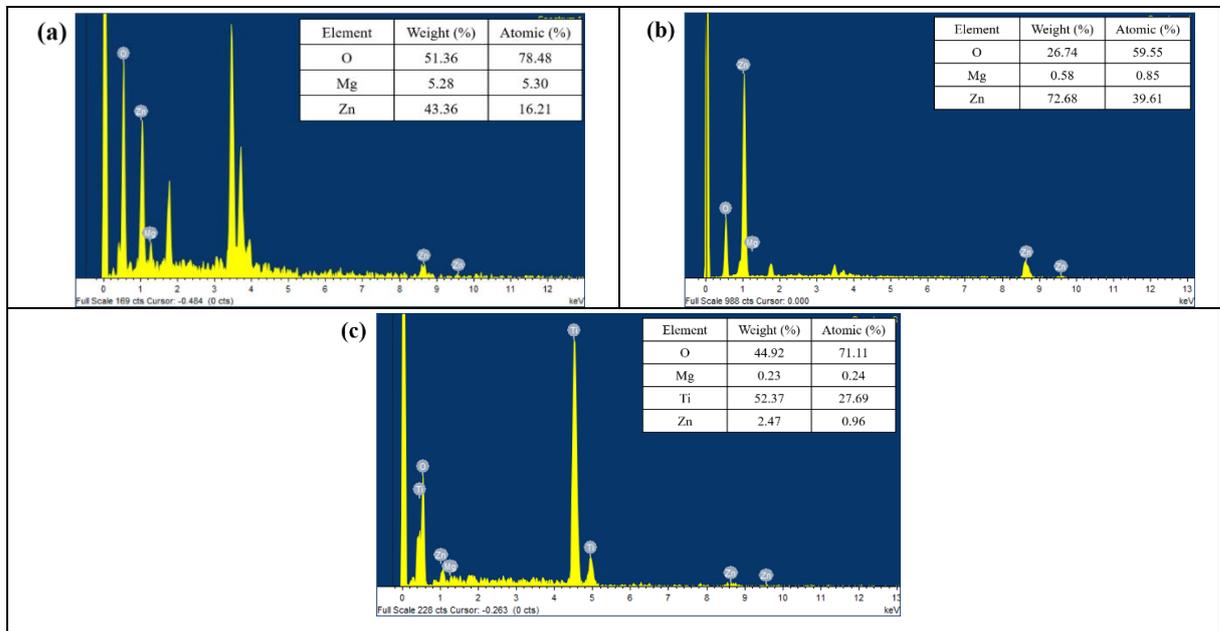


Fig. 2. EDX spectra of (a) MgZnO seeded catalyst, (b) ZnO and (c) ZnO/TiO₂ bilayer.

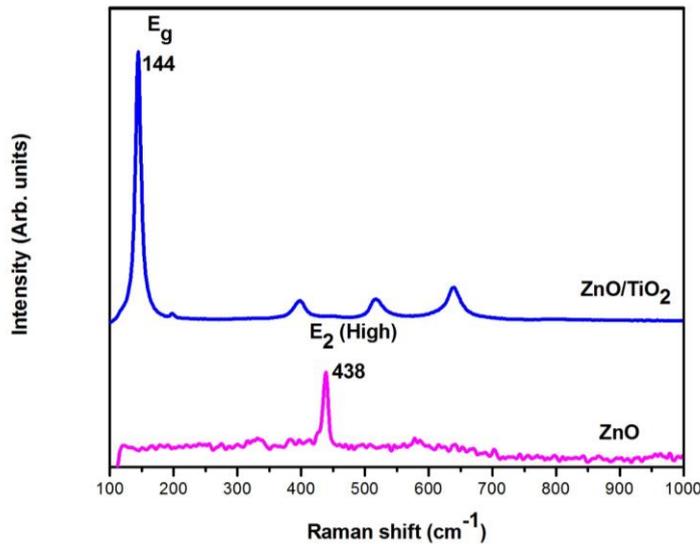


Fig. 3. Raman spectra of ZnO and ZnO/TiO₂ bilayer.

The structural properties were further analysed by micro-Raman spectroscopy as shown in Fig. 3. Based on Raman analysis, it shows peaks and

phases of ZnO and ZnO/TiO₂ bilayer which could determine the defects and qualities of crystal (Ahmed, et al, 2011). The ZnO nanorods have peak at 438

cm⁻¹ E₂ (high) that explained a wurtzite phase in ZnO structure. This Raman spectra also explained the peaks of ZnO/TiO₂ bilayer which has prominently intense peak at 144 cm⁻¹ (Ohsaka, et al, 1980).

CONCLUSION

The ZnO/TiO₂ bilayer was successfully fabricated as photoanode for future application in DSSCs. The structural properties of ZnO/TiO₂ bilayer had been investigated by using FESEM, EDX and micro-Raman spectroscopy. The FESEM images show that the structure of ZnO/TiO₂ bilayer had large surface area in nanoparticles surface to increase the dye loading in photoanode. Whereas, the EDX spectra confirmed that the ZnO/TiO₂ bilayer thin film had the Mg, Zn, Ti and O elements. Then, the micro-Raman spectra explained the crystallinity structure of ZnO/TiO₂ bilayer. Therefore, according to the structural properties of ZnO/TiO₂ bilayer, it showed that ZnO/TiO₂ bilayer can be applied for photoanode in DSSCs.

ACKNOWLEDGMENTS

The authors express thanks to TWAS-COMSTECH Research Grants (2017-0001-102-11), FRGS (2015-0154-102-02) and NND (2014-0015-102-03) grants for financial support.

REFERENCES

- Ahmed, F., S. Kumar, N. Arshi, M.S. Anwar, and R. Prakaash. 2011. Growth and Characterization of ZnO Nanorods Microwave-Assisted Route: Green Chemistry Approach. *Advanced Materials Letters*. 2:183-187.
- Fan, J., Y. Hao, C. Munuera, M. G-Hernandez, F. Guell, E. M. J. Johannsson, G. Boschloo, A. Hagfeldt, and A. Cabot. 2013. Influence of the Annealing Atmosphere on the Performance of ZnO Nanowire Dye-Sensitized Solar Cells. *Journal of Physical Chemistry C*. 117:16349-16356.
- Han, J., F. Fan, S. Lin, M. Wei, X. Duan, and L. Wang. 2010. ZnO Nanotube-Based Dye-Sensitized Solar Cell and its Application in Self-Powered Devices. *Nanotechnology*. 21:405203 1-405203 7.
- Kim, C. E., P. Moon, S. Kim, J-M. Myoung, H. W. Jang, J. Bang, and I. Yun. 2010. Effect of Carrier Concentration on Optical Bandgap Shift in ZnO:Ga Thin Films. *Thin Solid Films*. 518:6304-6307.
- Kislyuk, V. V., and O. P. Dimitriev. 2008. Nanorods and Nanotubes for Solar Cells. *Journal of Nanoscience and Nanotechnology*. 8:131-148.
- Kwiatkowski, M., I. Bezverkhyy, and M. Skompska. 2015. ZnO Nanorods Covered with TiO₂ Layer: Simple Sol-Gel Preparation, Optical, Photocatalytic and Photoelectrochemical Properties. *Journal of Materials Chemistry A*. 3:12748-12760.
- Lee, Y., J. Chae, and M. Kang. 2010. Comparison of the Photovoltaic Efficiency on DSSC for Nanometer Sized TiO₂ using a Conventional So-Gel and

- Solvothermal Methods. *Journal of Industrial and Engineering Chemistry*.16:609-614.
- Li, Z., Y. Zhou, G. Xue, T. Yu, J. Liu and Z. Zou. 2012. Fabrication of Hierarchically Assembled Microspheres Consisting of Nanoporous ZnO Nanosheets for High-Efficiency Dye-Sensitized Solar Cells. *Journal of Materials Chemistry*. 22:14341-14345.
- Lien, S-T., J-Z. Chen, Y-J. Yang, C-C. Hsu, and I-C. Cheng. 2014. Sol-Gel Derived Amorphous/Nanocrystalline MgZnO Thin Films Annealed by Atmospheric Pressure Plasma Jets. *Ceramics International*. 40:2707-2715.
- Malek, M. F., M. H. Mamat, M. Z. Sahdan, M. H. Zahidi, Z. Khusami, and M. R. mahmood. 2013. Influence of Various Sol Concentration on Stress/Strain and Properties of ZnO Thin Film Synthesized by Sol-Gel Technique. *Thin Solid Films*. 527:102-109.
- Malek, M. F., M. H. Mamat, T. Soga, S. A. Rahman, S. A. Bakar, A. S. Ismail, R. Mohamed, S. A. H. Alrokayan, H. A. Khan, and M. R. Mahmood. 2016. Thickness-Controlled Synthesis of Vertically Aligned c-Axis Oriented ZnO Nanorod Arrays: Effect of Growth Time via Novel Dual Sonication Sol-Gel Process. *Japanese Journal of Applied Physics*. 55:01AE15 1-01AE15 6.
- Ohsaka, T. 1980. Temperature Dependence of the Raman Spectrum in Anatase TiO₂. *Journal of the Physical Society of Japan*. 48:1661-1668.
- Ozgur, U., I. Alivov, C. Liu, A. Teke, M. A. Reshchikov, S. Dogan, V. Avrutin, S-J. Cho, and H. Morkoc. 2005. A Comprehensive Review of ZnO Materials and Devices. *Journal of Applied Physics*. 98:041301 1-041301 103.
- Suriani, A. B., R.N. Safitri, A. Mohamed, S. Alfarisa, I.M. Isa, A. Kamari, N. Hashim, M.K. Ahmad, M.F. Malek, and M. Rusop. 2015. Enhanced Field Electron Emission of Flower-Like Zinc Oxide on Zinc Oxide Nanorods Grown on Carbon Nanotubes. *Materials Letters*. 149:66-69.
- Suriani, A. B., A.R. Dalila, A. Mohamed, M.H. Mamat, M.F. Malek, T. Soga, and M. Tanemura. 2016. Fabrication of Vertically Aligned Carbon Nanotubes-Zinc Oxide Nanocomposites and their Field Electron Emission Enhancement. *Materials and Design*. 90:185-195.
- Tan, W. K., Z. Lockman, K. A. Razak, G. Kawamura, H. Muto, and A. Matsuda. 2013. Enhanced Dye-Sensitized Solar Cells Performance of ZnO Nanorod Arrays Grown by Low-Temperature Hydrothermal Reaction. *International Journal of Energy Research*. 37:1992-2000.
- Tang, H., K. Prasad, R. Sanjines, P. E. Schmid, and F. Levy. 1994. Electrical and Optical Properties of TiO₂ Anatase Thin Films.

- Journal of Applied Physics. 75:2042-2047.
- Umar, A., M. M. Rahman, S. H. Kim, and Y-B. Hahn. 2008. Zinc Oxide Nanonail Based Chemical Sensor for Hydrazine Detection. *Chemical Communications*. 2:166-168.
- Valsaraj, D., M.R. Subramanian, and D. Kumaresan. 2016. Effect of Organic Binders of TiO₂ Pastes in the Photoanodes of Cost-Effective Dye Sensitized Solar Cells Fabrication. *Austin Chemical Engineering*. 3:1-6.
- Wu, D., Z. Gao, F. Xu, J. Chang, W. Tao, J. He, S. Gao, and K. Jiang. 2013. Hierarchical ZnO Aggregates Assembled by Orderly Aligned Nanorods for Dye-Sensitized Solar Cells. *Crystal Engineering Communications*. 15:1210-1217.
- Wu, Y., D. Liu, N. Yu, Y. Liu, H. Liang, and G. Du. 2013. Structure and Electrical Characteristics of Zinc Oxide Thin Films Grown on Si (111) by Metal-organic Chemical Vapor Deposition. *Journal of Materials Science and Technology*. 29:830-834.
- Xu, C-H., Y. F. You, J. Z. Wang, S. F. Ge, W. K. Fong, K. Leung, and C. Surya. 2013. Growth Behavior of ZnO Nanowires on Au-Seeded SiO₂-GaN co-Substrate by Vapor Transport and Deposition. *Superlattices and Microstructures*. 61:97-105.
- Yune, J. H., I. karatchevtseva, and G. Triani. 2013. A Study of TiO₂ Binder-Free Paste Prepared for Low Temperature Dye-Sensitized Solar Cells. *Journal of Material Research*. 28: 488-496.
- Zainun, A. R., S. Tomoyo, U.M. Noor, M. Rusop, and I. Masaya. 2012. New Approach for Generating Cu₂O/TiO₂ Composite Films for Solar Cell Applications. *Material Letters*. 66:254-256.
- Zeng, Y., T. Zhang, L. Wang, M. Kang, H. Fan. R. Wang, and Y. He. 2009. Enhanced Toluene Sensing Characteristics of TiO₂-doped Flowerlike ZnO Nanostructures. *Sensors and Actuators B: Chemical*. 140:73-78.
- Zhou, H., G. Fang, N. Liu, and X. Zhao. 2011. Ultraviolet Photodetectors Based on ZnO Nanorods-Seed Layer Effect and Metal Oxide Modifying Layer Effect. *Nanoscale Research Letters*. 6:1471-1476.